



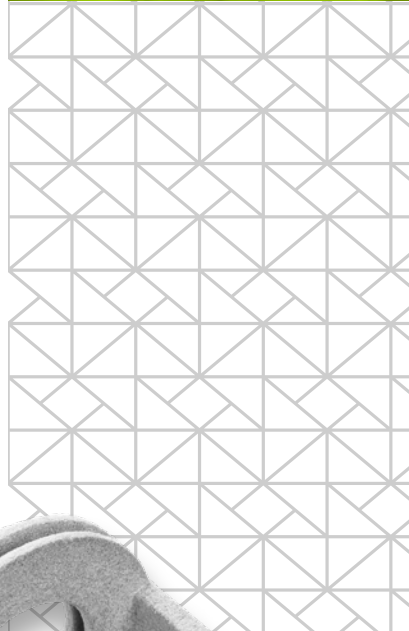

MATERIAL DATA SHEET
SAF

Stratasys SAF™ PA12

Extended Material Datasheet

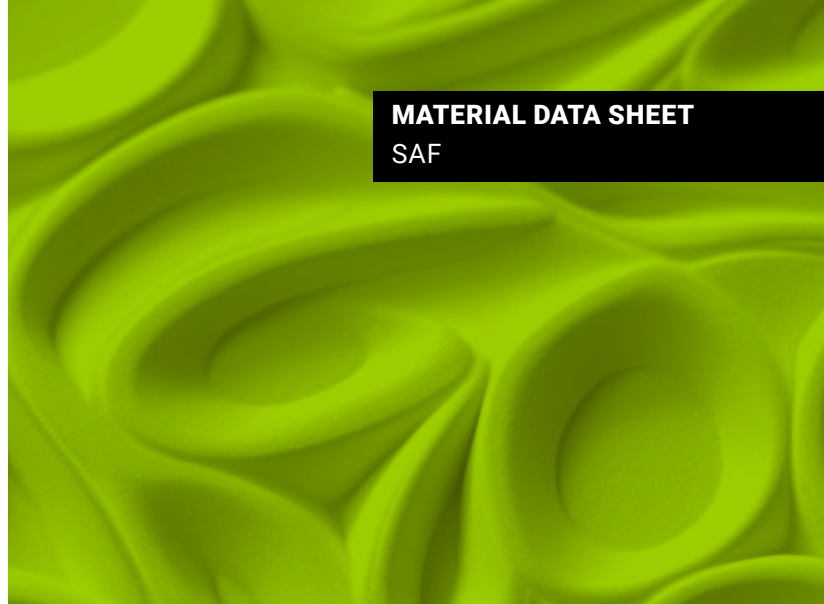



Overview

Processed with SAF™ technology on the Stratasys H350™ 3D printer, Stratasys SAF PA12 delivers production-grade plastic parts for high-volume demands – driving new areas of business growth. Stratasys SAF PA12 enables a high nesting density while maintaining high part consistency to deliver production-level yields.

Contents:

Mechanical Properties.....	3
Geometric Properties	7
Physical Properties.....	9



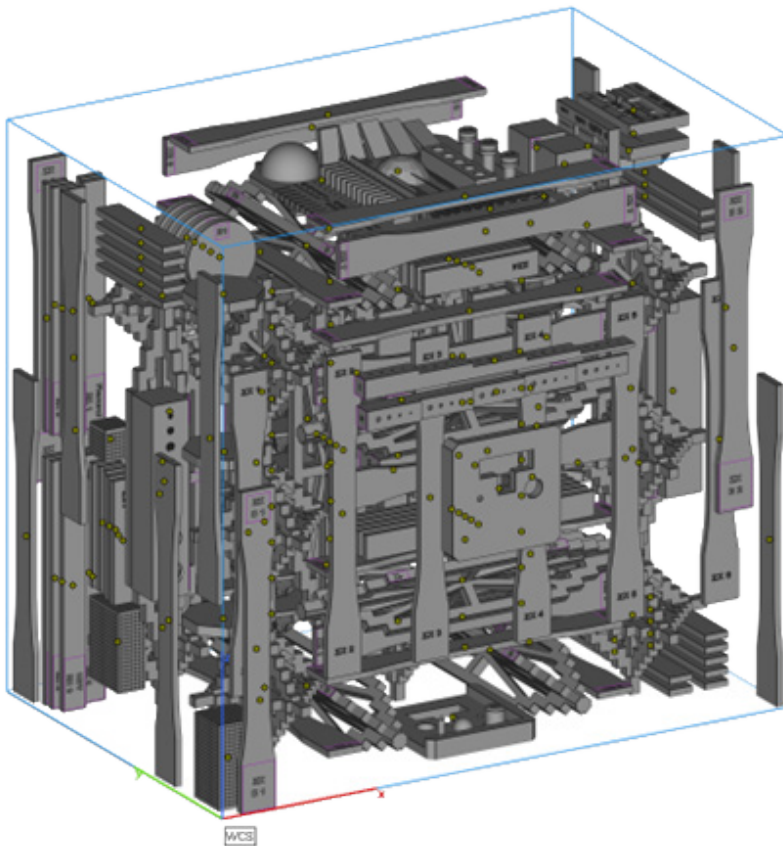


Figure 1: The Full Standard Test Build designed for PA12

Mechanical Properties

The mechanical data in this datasheet were generated from parts in the “Full Standard Test Build” (Figure 1) built using Stratasys SAF PA12, processed using SAF™ technology on the Stratasys H350. The “Full Standard Test Build” is robust in that it tests both mechanical and geometric performance from within the same build. However, the build itself has been modified to focus on specific customer PA12 requests (more accuracy, less mechanical data compared to the High Yield PA11 FSTB).

Comprehensive Sample Sizes

The mechanical data come from over 750 tensile specimens (>350 in X/Y and >350 in Z), 90 flexural specimens (60 in X/Y and 30 in Z) and 540 impact specimens (360 in X/Y and 180 in Z), all printed in 22 builds from 5 different printers split between 2 locations. Each build has 18 tensile specimens in the ZX orientation and 20 collectively in the X and Y orientations.



Standard Build and Test Practices

The build was prepared using GrabCAD Print Pro. The parts were built with standard machine settings following the H350 installation process. The material consisted of 70% used and 30% virgin powder by mass, as per PA12 H350 guidelines. Post processing of parts followed H350 guidelines including 24 hours cooling after removal from the machine, manual breaking out, and powder removal via automated bead blasting. No further post processing was performed. All testing was based on ASTM or ISO standards where applicable. All parts were preconditioned according to ASTM D618-13.

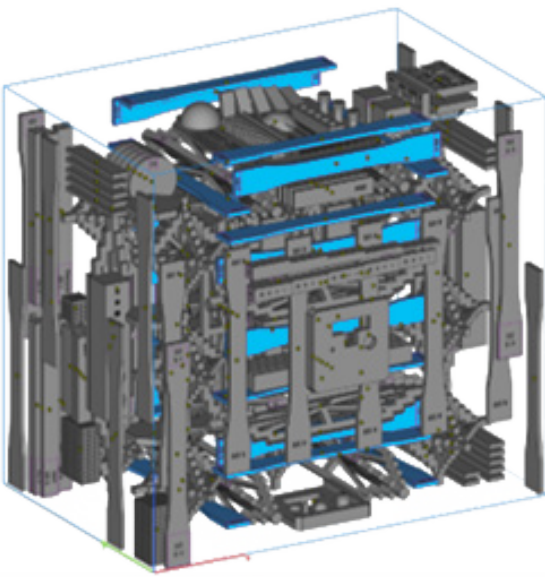


Figure 2: The placement of the X/Y tensile specimens shown for the full build (above) and tensile only (below)



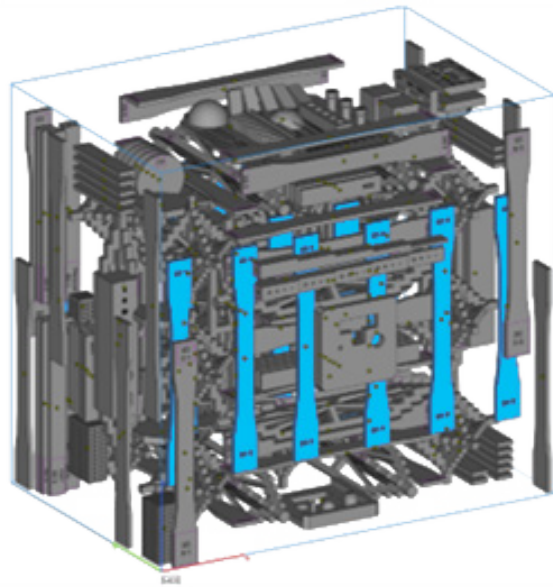


Figure 3: The placement of the ZX tensile specimens shown for the full build (above) and tensile only (below)

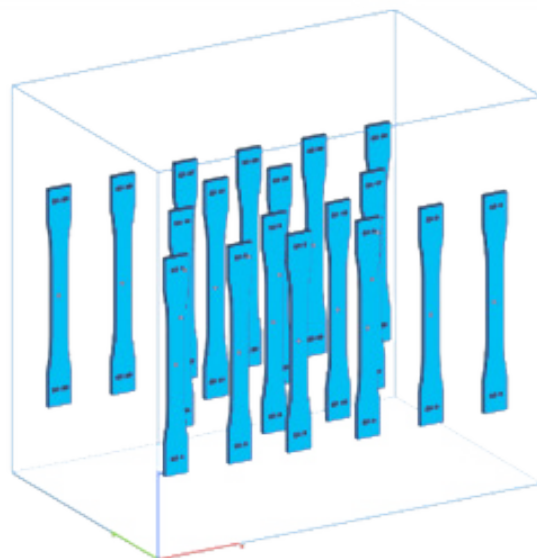

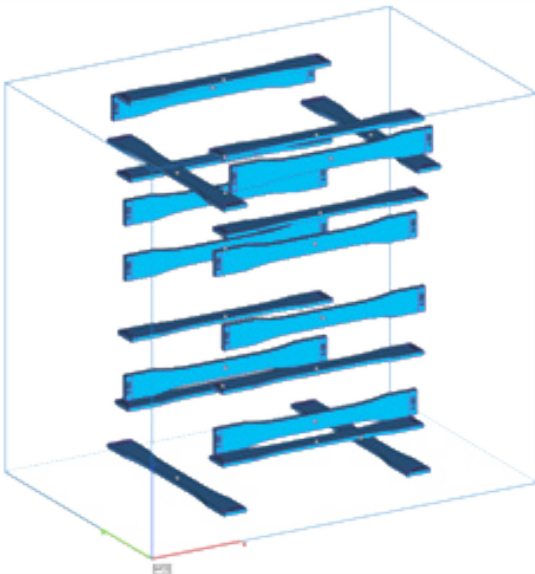

Full Build Characterization

The “Full Standard Test Build” contains a wide spread of ASTM D638-14 Type 1 tensile specimens in three orientations: ZX (upright), XZ (on end) and XY/YX (laid flat).

The 20 XY, XZ and YX specimens (highlighted in Figure 2) and the 18 ZX specimens (highlighted in Figure 3) are comprehensively placed within the test build, allowing full characterization of the build volume and real confidence in the mechanical performance of the H350.

The test build also contains geometric property specimens, physical property specimens and give-away parts at a part nesting density of 12%.



Property	Mean	Standard Deviation	Unit	Standard
Tensile Strength (XZ,YX)	47 (6817)	2.3 (754)	MPa (psi)	ASTM D638-14
Tensile Strength (ZX)	45 (6672)	2.2 (319)	MPa (psi)	ASTM D638-14
Elongation at Break (XZ,YX)	11	2.2	%	ASTM D638-14
Elongation at Break (ZX)	6	1.7	%	ASTM D638-14
0.2% Offset Yield Strength (XZ,YX)	33.5 (4859)	-	MPa (psi)	ASTM D638-14
0.2% Offset Yield Strength (ZX)	32.2 (4670)	-	MPa (psi)	ASTM D638-14
Tensile Modulus (XZ,YX)	1750 (254)	100 (14)	MPa (ksi)	ASTM D638-14
Tensile Modulus (ZX)	1700 (247)	100 (14)	MPa (ksi)	ASTM D638-14
Flexural Strength (XZ,YX)	54 (7816)	2 (271)	MPa (psi)	ASTM D790-17
Flexural Strength (ZX)	57 (8272)	1 (169)	MPa (psi)	ASTM D790-17
Flexural Modulus (XZ,YX)	1405 (208)	60 (8.7)	MPa (ksi)	ASTM D790-17
Flexural Modulus (ZX)	1525 (221)	29.7 (4.3)	MPa (ksi)	ASTM D790-17
Notched Impact Strength (XZ,YX)	4.17 (1.98)	-	kJ/m ² (Ft.lbf/in ²)	ASTM D256-10
Notched Impact Strength (ZX)	3.36 (1.6)	-	kJ/m ² (Ft.lbf/in ²)	ASTM D256-10



Mechanical Properties

The below histograms visualize the mechanical data presented in this datasheet:

Ultimate Tensile Strength (UTS)

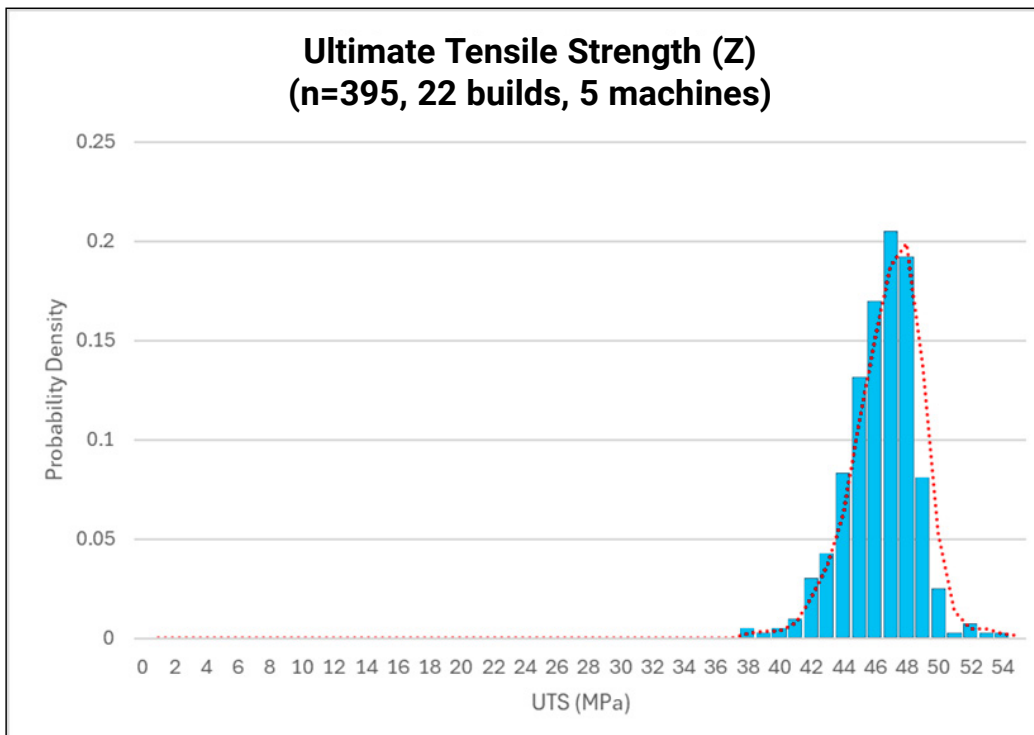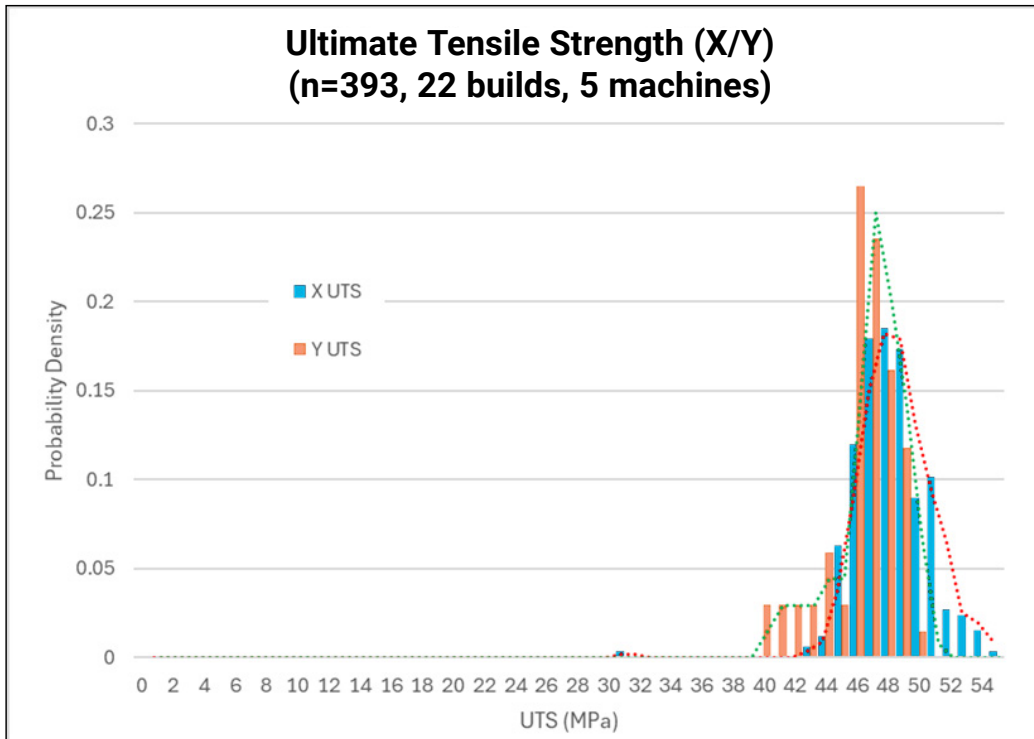



Geometric Properties

The following geometric data were generated from the same builds as the previous mechanical data, made possible by the H350's ability to make both strong and accurate parts with the same settings. All parts were built and post-processed using the same standard methods as stated in the mechanical section. All parts were measured with a Aberlink EXTOL 370 CMM. The geometric data comes from a geometric "star" (nominal range from 5 to 80mm). The placement of these star parts can be seen in Figure 4.




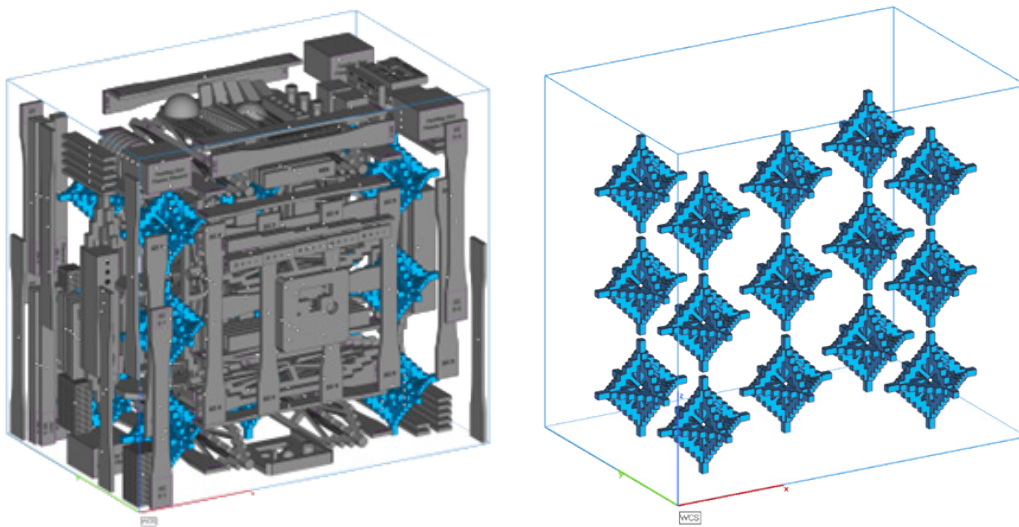


Figure 4: The placement of the geometric specimens within the full test build (left) and placement of the 15 geometric specimens only (right)

The below histograms visualize the geometric data presented in this datasheet – split into X, Y and Z measurements.

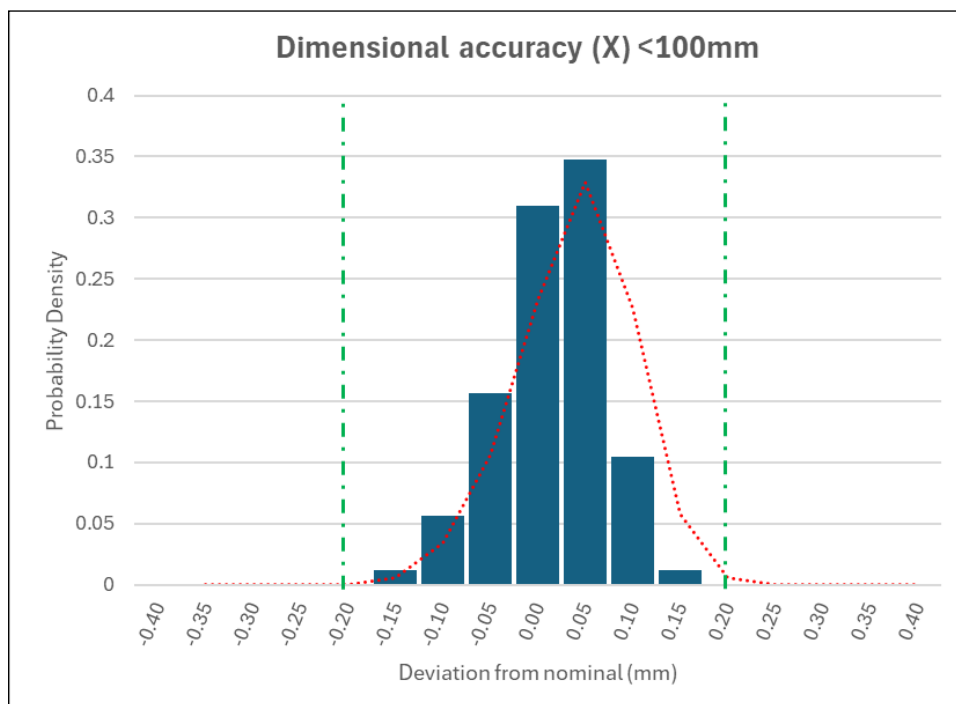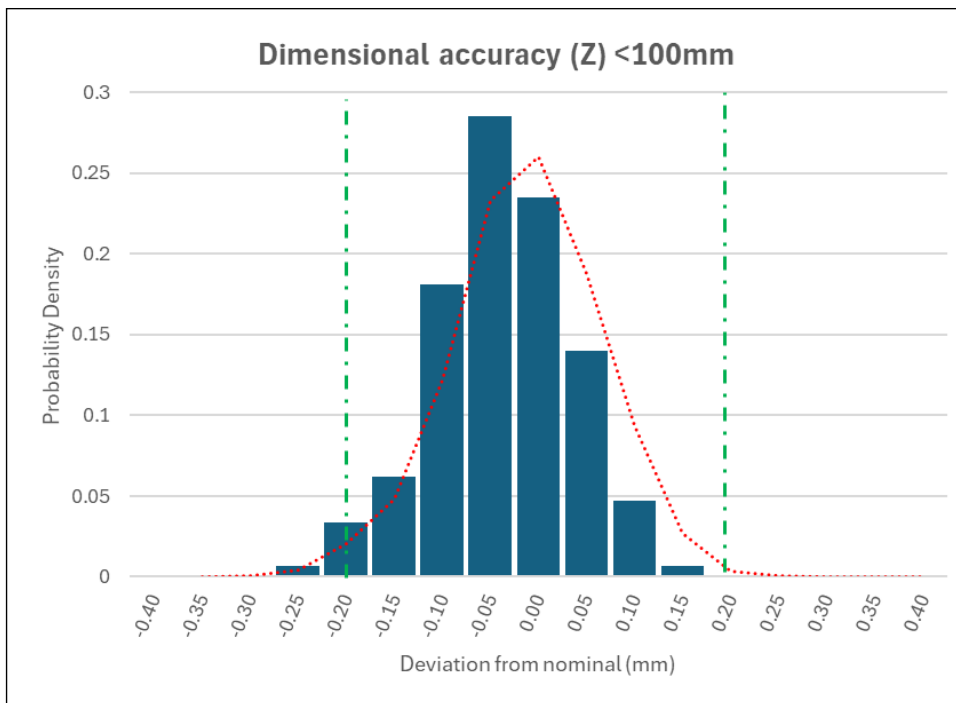

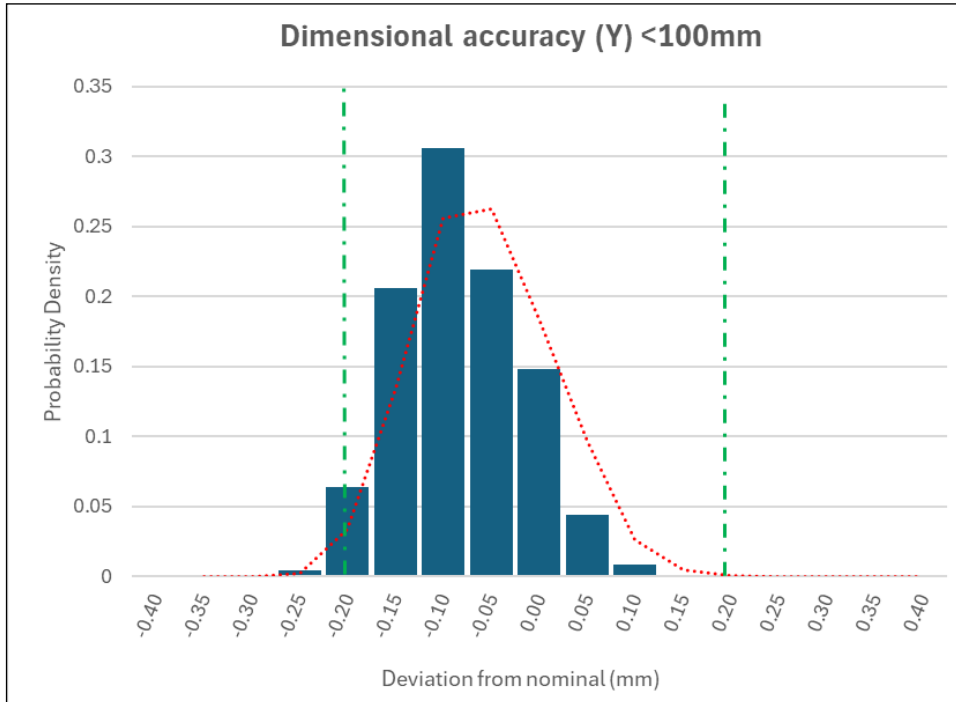

Tolerance	Yield (XY)	Yield (Z)
$\pm 200\mu\text{m}$ (8 thou)	96.6%	95.8%



Physical Properties

General	Value	Unit	Standard
Part Specific Gravity	0.98	-	ASTM D792-13
Virgin Particle Size D50	56 (2.2)	µm (thou)	-
Virgin Powder Melting Point	185 (365)	°C (°F)	-
Thermal	Mean	Unit	Standard
Heat Deflection Temperature (0.45MPa/65psi)	173 (343)	°C (°F)	ASTM D648
Heat Deflection Temperature (1.82MPa/264psi)	77 (171)	°C (°F)	ASTM D648
Coefficient of Thermal Expansion	160 (0.089)	µm/°C.m (thou/in.°F)	ASTM E831
Specific Heat Capacity (20°C/68°F)	1.69 (0.4)	J/g.°C (BTU/lbm.°F)	ASTM E1952
Thermal Conductivity (23°C/68°F)	0.192 (1.34)	W/°C.m (BTU/hr.ft.°F)	ASTM E1952
Electrical	Mean	Unit	Standard
Surface resistivity	5.53 x10 ¹³	Ohm	ASTM D257
Volume resistivity	4.19 x10 ¹⁴	Ohm-cm	ASTM D257
Bio compatibility	Result	Unit	Standard
Determination of Sensitization - human cell line activation test (h-Clat)	Non-Sensitizer	N/A	OECD 442E 2018-06
Determination of Skin Irritation	Non-irritant	N/A	ISO 10993-10 2014-10 / OECD 439 2015-07
Determination of Cytotoxicity	Material shows no cytotoxic effect	N/A	DIN EN ISO 10993-5, 2009, Annex D
Flammability	Mean	Unit	Standard
UL94 HB	Pass*	Not Applicable	UL94 (2013)
Reusability	Value	Unit	Standard
Typical Powder Mix Ratio (Virgin)	30	%	-

* Product is not currently UL Blue Card Registered.

Disclaimer:

¹ Customer acknowledges the contents of this document and that Stratasys parts, materials, and supplier are subject to its standard terms and conditions, available on <http://www.stratasys.com/legal/terms-and-conditions-of-sale>, which are incorporated herein by reference.

² The specifications and/or information on which this document is based are subject to change without notice.

³ The information presented are typical values intended for reference and comparison purposes only. They should not be used for design specifications or quality control purposes. End-use material performance can be impacted (+/-) by, but not limited to, part design, end-use conditions, test conditions, etc. Actual values will vary with build conditions. Tested parts were built on the Stratasys H350 3D printer. Product specifications are subject to change without notice. The performance characteristics of these materials may vary according to application, operating conditions, or end use. Each user is responsible for determining that the Stratasys material is safe, lawful, and technically suitable for the intended application, as well as for identifying the proper disposal (or recycling) method consistent with applicable environmental laws and regulations. Stratasys makes no warranties of any kind, express or implied, including, but not limited to, the warranties of merchantability, fitness for a particular use, or warranty against patent infringement.



stratasys.com

ISO 9001:2015

Certified

Stratasys Headquarters

7665 Commerce Way,

Eden Prairie, MN 55344

+1 800 801 6491 (US Toll Free)

+1 952 937-3000 (Intl)

+1 952 937-0070 (Fax)

1 Holtzman St., Science Park,

PO Box 2496

Rehovot 76124, Israel

+972 74 745 4000

+972 74 745 5000 (Fax)

MATERIAL DATA SHEET SAF

© 2024 Stratasys. All rights reserved. Stratasys, the Stratasys Signet logo, Stratasys Direct Manufacturing, H350, H Series, SAF, Selective Absorption Fusion, Big Wave and HAF are trademarks or registered trademarks of Stratasys Inc. and/or its affiliates. The H350 printer is subject to a license from Loughborough University Enterprises Limited and Evonik IP GmbH under the following and/or related patents and patent applications and their family members: EP2739457, EP3539752, EP1648686, EP 1740367, EP1737646, EP1459871. Further details including live and in-force status of family members may be found at <https://worldwide.espacenet.com/patent/search/family>. All other trademarks are the property of their respective owners, and Stratasys assumes no responsibility with regard to the selection, performance, or use of these non Stratasys products. Product specifications subject to change without notice. MDS_SAF_PA12 extended_0724a